

Issue 1/2007

Profi Tip

Rollers in Inking and Dampening Systems



Print Media Academy

HEIDELBERG

Foreword



Bernd Schopp,
Director of the
Print Media Academy

Dear Reader, in our current Profi Tip we focus on the inking and dampening systems of your Heidelberg presses. We give you some information on the critical importance of the rollers for the quality and efficiency of your print processes.

The articles explain the principles of the manufacture and use of rollers. And we answer the question of how they have to be inserted, adjusted and maintained. Using this knowledge you can make cost savings and will obtain an impressive consistency of print quality. On top of that, you will increase roller service life as well as print shop productivity. We are sure you will find this of great interest.

Yours, Bernd Schopp

Contents

Roller Manufacture	3	Quickmaster QM 46-2	16
Shore Hardness	4	Printmaster GTO with	
Roller Maintenance	6	Direct Film Dampening System	17
Glazing	7	Printmaster PM 52/Speedmaster SM 52	18
Inking/Dampening System Adjustment	8	Printmaster PM 74 with Ecocolor	19
Press Strip Adjustment	9	Speedmaster SM 74 with Alcolor	20
Alcolor Dampening System	10	Speedmaster CD 74	21
Alcolor Dampening System Adjustment	11	Speedmaster SM 102/CD 102	22
Pre-/Post-Dampening with Alcolor	12	Speedmaster XL 105	
IPA-Free Ecocolor Dampening System	14	Hycolor Ink and Dampening System	23

Roller Manufacture



Synthetic rubber is used in roller manufacture: a complex mix of natural rubber and various chemicals that obtain their stability and elasticity through the vulcanization process. It is the raw rubber that gives the rubbery material its basic characteristics. To this are added the vulcanization

agents for the subsequent vulcanization process. Plasticizers (fluid oils) play a major role as they – along with the extenders and the vulcanization agents – determine the subsequent degree of hardness of the material. The more plasticizers are added, the softer the rubber after the vulcanization process.

- If possible, do not expose rollers to direct natural or artificial light.
- The special paper that the rollers come delivered in prevents light penetrating and therefore helps retain the rubber's characteristics. For this reason, do not remove the paper before inserting the roller in the printing press.
- Always put the roller with its pivots on a frame support: Putting it down directly onto the rubber can result in permanent deformations (pressure marks).
- Store rubber rollers in a cool and dry place.
- Under certain circumstances ozone causes microscopic scratches on the rubber surface. For this reason do not store rollers in the vicinity of motors or other electrical devices.

Shore Hardness

- In line with their task of transferring ink, **inking rollers** must be adjusted to be oil-friendly (or oleophilic). In an inking system with conventional inks, rollers of Shore A hardness between 30° and 35° are used. For UV inks, rollers with Shore A hardness of 25° and between 40° and 45° are used.
- **Dampening rollers** should be water-friendly (hydrophilic). For alcohol dampening systems, Shore A hardness of between 25° and 30° is suitable. In direct dampening systems, hard rubber rollers are used.



The Shore hardness of a roller determined with a Shore meter designates the resistance against penetration of a needle taking the form of either a conic section (Shore A) or a point (Shore D), pressed with a defined force (1 kp) for a period of three seconds against the rubber surface. Soft rollers are measured with Shore A, and hard rollers with Shore D. The general hardness tolerances according to DIN/EN are +/- 5° Shore A

Shore hardness can be easily measured and gives the printer information on the condition of the rollers. Rollers tend to become harder with use, as they are exposed to inks, dampening agents and detergents, as well as the atmosphere. Additional hardening of 5° Shore in the first months of use should be regarded as normal. Accelerated hardening in use can be a sign that the rollers are gradually shrinking. If you adjust a roller that has been subject to hardening and shrinkage to its original gap width, it may well be that its original transfer characteristics will be reproduced. At the same time, however, the gap width is closer than previously. This leads to higher pressure and higher temperatures – and thereby to higher wear on the roller.

Increased hardness can also indicate that a hard film of paper coating and dampening agents has become deposited on the roller surface. This film should be regularly removed to prevent the roller hardening and glazing with use. **The clean and satin-like surface of a roller is even more important than its hardness.**

Roller Maintenance

For optimum maintenance of rollers, the roller manufacturers recommend a universal group AIII agent that can be mixed with water. Alternatively, high solids alkyd resins or biological detergent may be used. Long service life of the rollers can only be achieved with proper handling and maintenance. (On UV printing, the service-life is as a rule shorter.)



Ageing cracks



Ozone cracks




Cracking due to chemicals

- The choice of detergent plays an essential role in roller service life. Highly volatile cleaners remove the plasticizer from the rubber, which leads to shrinkage and hardening. Other possible consequences of using unsuitable detergents are swollen rollers or corroded hoses, seals, machinery paintwork and blankets. Suitable detergents are certified by FOGRA and may be selected from the relevant list (cf. www.fogra.org).
- Various applications (standard inks, UV, hybrid) each require specific roller materials and these in turn require detergents that are specially suited to them.
- Along with print chemicals that affect the roller directly, external factors such as UV light, damp and room temperature may result in premature ageing of the rubber.

Glazing

Over time, rollers pick up particles from the ink, the paper coating and the dampening agent which block their pores. This contamination results in a smooth shiny surface. Inappropriate detergents and hard water contribute to this effect. Transfer of ink and dampening solution is noticeably inhibited as a result.

By using a special decalcifying agent, scaling can be removed and the rollers regenerated. It is recommended you discuss with the roller manufacturer which agents have the least long-term effects on the rubber.

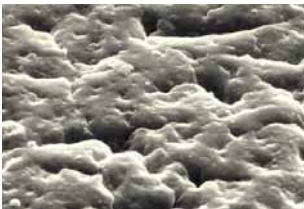


Clean roller with porous surface



Glazed roller with calcification on the surface


Inking/Dampening System Adjustment

- Carry out adjustment work on rollers once they have run warm, or else calculate in an increase of the adjustment strips.
- As a rule, set the damping form roller and inking form roller nearer to the distributor than to the printing plate – but not so near that a pressure strip in the form of a cigar occurs with the plate. This would indicate that the roller is being bent towards the cylinder channel.
- Only adjust the rollers according to manufacturer specifications.
- Always adjust from minus to plus, so as to eliminate thread play on adjustment.
- On “Vario“ set the ink form roller nearer to the distributor, so that it is decelerated by the dampener oscillator roller.
- When setting the ink form roller to the plate, high pressure is momentarily exerted (impact), which generates a stronger press strip. For precise adjustment of the print plate, first ink up and set down the rollers after waiting for around 10 seconds.
- Precise roller adjustment is best carried out via the press strip. For this, coat the rollers equally with a light-colored ink (yellow). After the ink has distributed and a waiting time of around 10 seconds, with a piece of paper squeeze off the press strip generated.
- Always measure between the dot fringes as these are more evident with increased ink.
- Always set the rollers parallel to each other (tolerance 0.5 mm).

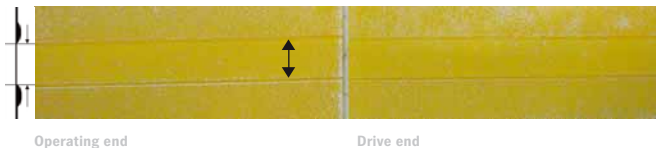

Press Strip Adjustment


Heidelberg provides an adjusting gauge which allows precise measurement of the press strips (can be ordered over the Internet at <http://www.heidelberg-selection.com> or via the relevant distributor, part no. G2.024.001). A paper template print of the press strip makes measuring easier and can be used for documentation purposes.

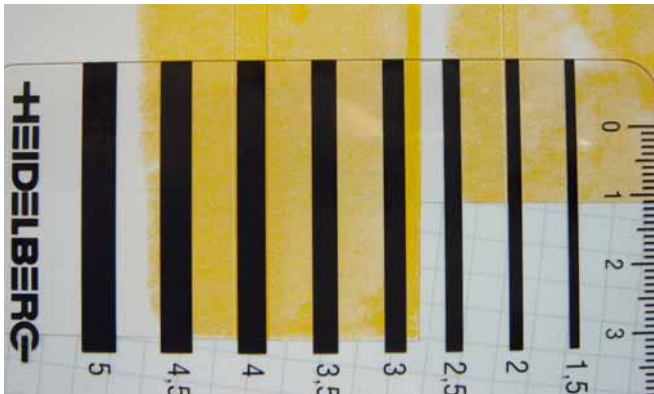

By making a professional adjustment, the printer ensures the right pressure between the rollers. This then ensures ink distribution and a consistent supply of dampening agent.

Alcolor Dampening System

- 12 | Dampening form roller
- 13 | Intermediate roller
- 14 | Tipping roller
- 15 | Application roller
- E | Dampener oscillator roller

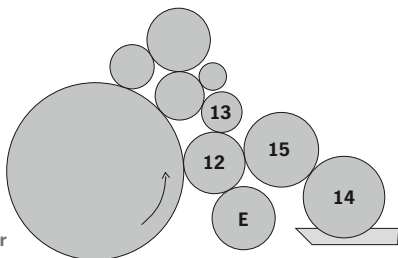


Print quality starts with the interaction of the inking and dampening system: Consistently good results assume a stable ink-water balance. Precise adjustment ensures thin and equal distribution of the dampening agent film on the printing plate. This reduces sheet drying time, allowing the sheets to get through the finishing process sooner.

A responsible printer checks the adjustments every three months and adjusts in line with the operating manual.

The dampening agent ideally has a water hardness of 8° to 12° on the German scale (dH) and a pH value of 4.8 to 5.5. The usual dampening agent temperature is deemed to be between 10°C and 15°C. To prevent the occurrence of print problems, it is recommended that the dampening agent be renewed every 14 days.

Alcolor Dampening System Adjustment

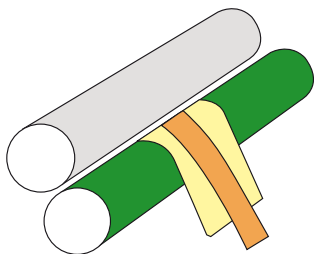


Basic adjustment of the dampening system should be performed with a clean roller with two thin paper strips (approximately 0.05 mm thick). The wide paper strip covers the rubber roller, while the narrow strip acts as a feeler gauge. This means that the greater resistance of the rubber roller is not felt. The narrow strip slips between the wide

paper strip and the smooth distributor roller. There is an exact description of the method in the operating instructions.

If the Alcolor dampening system is adjusted or checked with ink, be aware that when the strip is formed an unintended rolling movement occurs from the application roller to the damping form roller. This makes the press strip wider. If there is a suitable waiting time (approximately 30 seconds), the “inner” strip can be properly assessed.

12 | Damping form roller
15 | Application roller

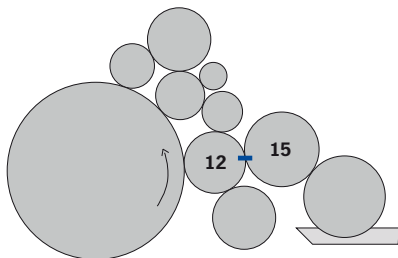


Pre-/Post-Dampening with Alcolor

Using automatic pre-dampening, the Alcolor dampening system ensures there is adequate dampening agent film on the printing plate. Where printing is interrupted (washing, stopper etc.) the dampening system is automatically switched off by the plate as part of a post-dampening phase. The duration of the automatic pre- and post-dampening phases can be set by via the machine control system and thereby adapted to the many different materials in use and the conditions that exist around the world. Good adjustment ensures an optimum amount of dampening agent when printing starts and after printing has been interrupted.

The pre- and post-dampening phase with Alcolor

Mode	Standard settings	Revolutions	Adjustment range max. revolutions	Adjustment range min. revolutions
Pre-dampening phase 1	3	3	18	0
Pre-dampening phase 2	2	2	18	0
Post-dampening phase 1	15	15	50	0
Post-dampening phase 2	45	45	100	0


To avoid excess dampening agent on the printing plate, the pre- and post-dampening phases should be set to the minimum.

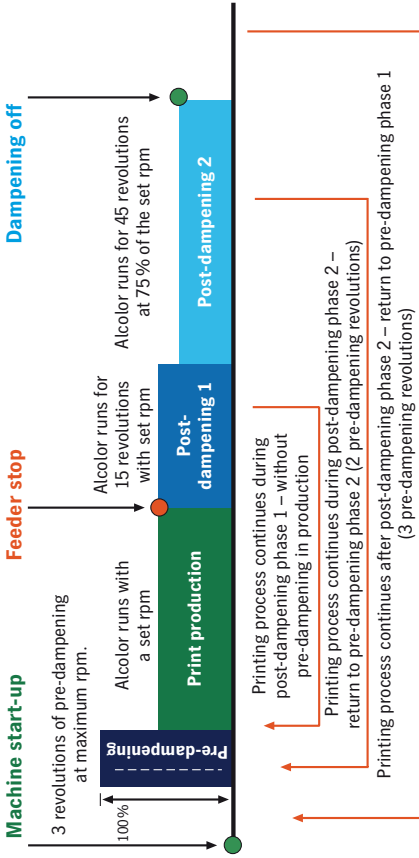

IPA-Free Ecocolor Dampening System

100% IPA-free printing with the Ecocolor dampening system reduces emissions, improves the print shop atmosphere and at the same time saves alcohol costs. Ecocolor ensures quick and stable ink/water balance. Dampening agent control is via a potentiometer. Dampening agent temperature is set to 18 to 20°C.

- 22 | Damping form roller
- 23 | Intermediate roller
- 24 | Tipping roller
- 25 | Application roller
- 26 | Transfer roller, large
- 27 | Transfer roller, small
- E1 | Dampener oscillator roller

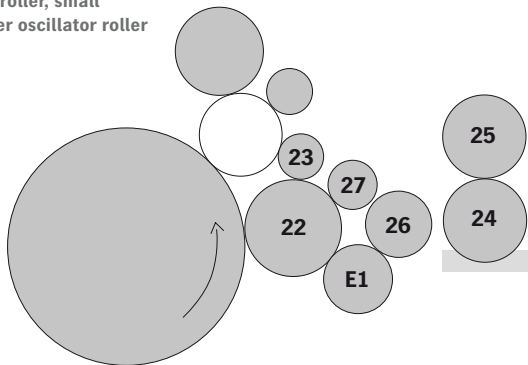


On IPA-free printing, the degreasing action of the alcohol in the dampening agent is not present. This means that oily detergent residues may remain on the rollers, and these can inhibit dampening agent transfer. This is why absolutely faultless washing procedures are needed. The basic cleaning agent must under no circumstances contain aromatic compounds, as these may damage the rollers. You should ask your ink supplier about a suitable cleaning agent.

A tip:

Clean the rollers by hand after each wash. To do this, run the press to wash speed, switch the intermediate roller on the press to connect by double-clicking (it flashes) and using a spray bottle, spray a water/alcohol mixture (80 % / 20 %) onto the rollers. Set wash-up blades via the service menu and wipe. Clean the tipping roller and applicator roller with alcohol (on the front surfaces as well).

Quickmaster QM 46-2

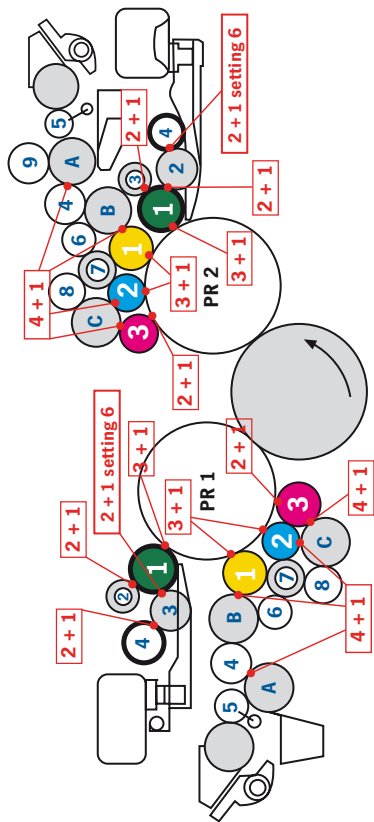

Roller diameter


Damping form roller | **63 mm**

1. Ink form roller | **54.7 mm**


2. Ink form roller | **45 mm**

3. Ink form roller | **50 mm**

Printmaster GTO with Direct Film Dampening System

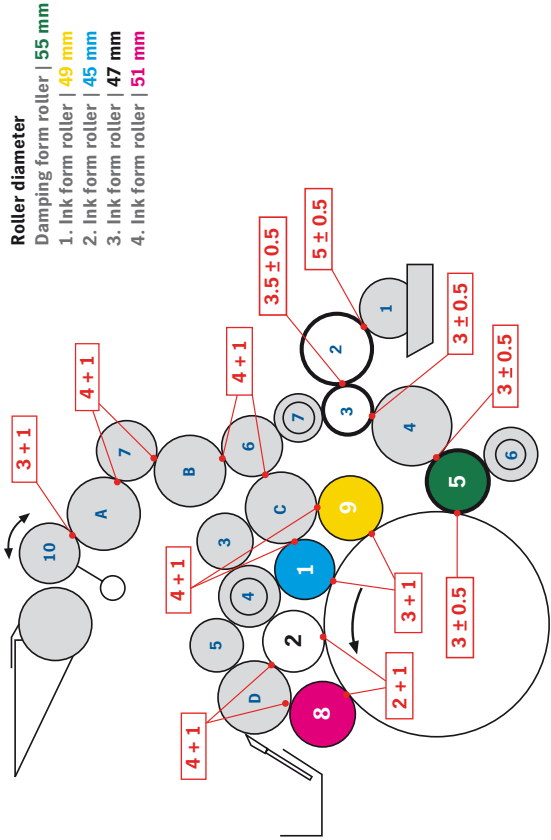

Printmaster PM 52/Speedmaster SM 52

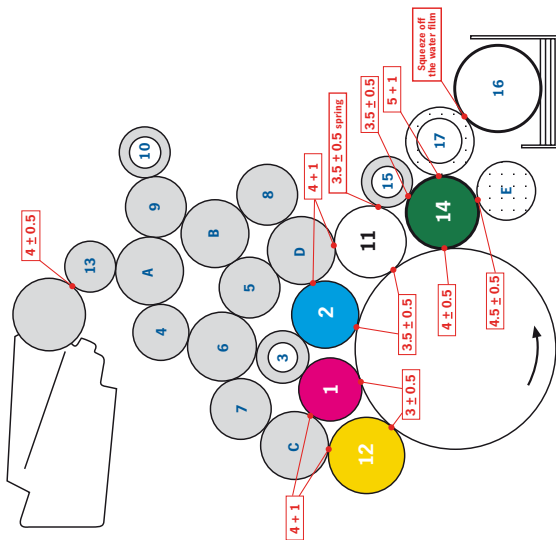

Roller diameter

Damping form roller | 68 mm

1. Ink form roller | 64.5 mm


2. Ink form roller | 61 mm

3. Ink form roller | 54 mm


4. Ink form roller | 68 mm

Printmaster PM 74 with Ecocolor

- Roller diameter**
Damping form roller | 75 mm
1. Ink form roller | 65 mm
2. Ink form roller | 60 mm
3. Ink form roller | 55 mm
4. Ink form roller | 70 mm

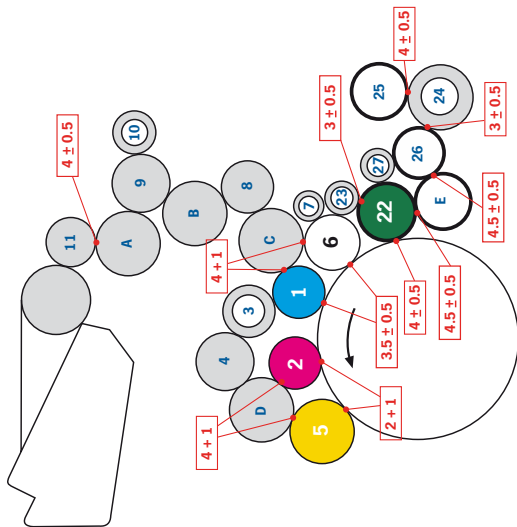

Speedmaster SM 74 with Alcolor

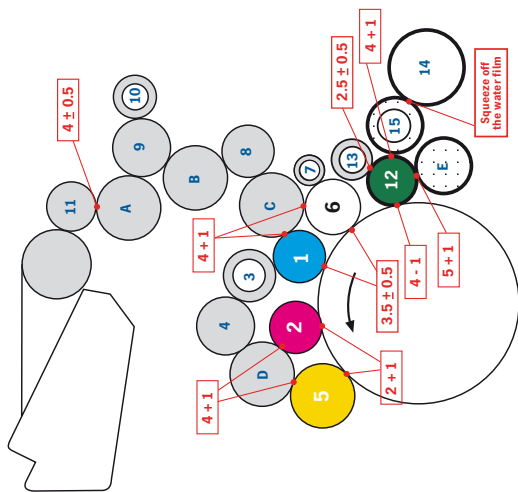

Roller diameter

Damping form roller | 48 mm


1. Ink form roller | 65 mm

2. Ink form roller | 60 mm

3. Ink form roller | 55 mm

4. Ink form roller | 70 mm

Speedmaster CD 74

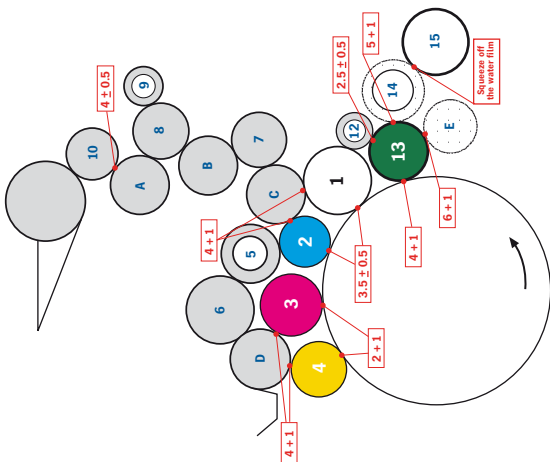

Roller diameter

Damping form roller | 70 mm

1. Ink form roller | 78 mm

2. Ink form roller | 60 mm

3. Ink form roller | 72 mm

4. Ink form roller | 66 mm

Speedmaster SM 102/Speedmaster CD 102

Roller diameter


Damping form roller | 78 mm

1. Ink form roller | 60 mm


2. Ink form roller | 72 mm

3. Ink form roller | 66 mm

4. Ink form roller | 80 mm

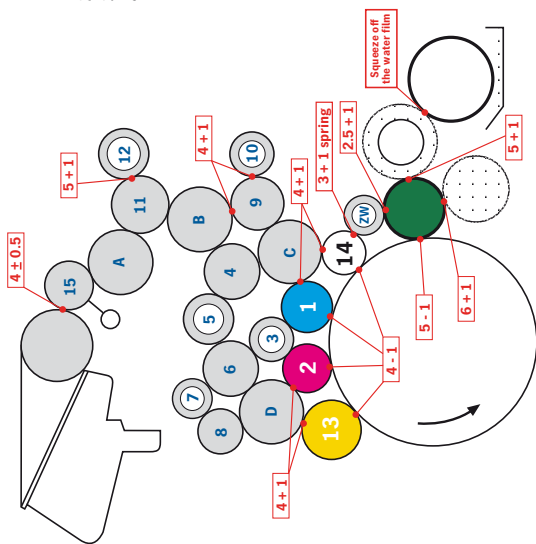

Speedmaster XL 105 Hycolor Inking and Dampening System

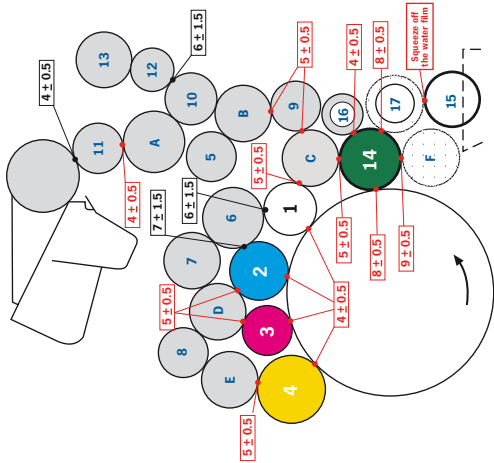

Roller diameter

Dampening form roller | **92 mm**

1. Ink form roller | **80 mm**

2. Ink form roller | **86 mm**

3. Ink form roller | **74 mm**

4. Ink form roller | **102 mm**

Are you missing a copy of Profi Tip from the Print Media Academy in your personal collection?



Issue 1/2005
Dampening Solutions in Offset Printing

Ausgabe 1/2005
Feuchtmittel im Offsetdruck



Issue 1/2006
Tips for Problem Cases in the Pressroom

Ausgabe 1/2006
Tipps bei Problemfällen im Drucksaal



Issue 1/2007
Rollers in Inking and Dampening Systems

Ausgabe 1/2007
Walzen in Farb- und Feuchtwerk

At www.print-media-academy.com you can order any past issue free of charge. Just tell us the issue and your address and you will get your personal copy directly.







In-Depth Knowledge: From Training on Machines to Management Seminars

The latest technologies and up-to-date management know-how from the print media industry – these are the two focal points of the comprehensive training and seminar provision of the Print Media Academy, which is represented in Germany and across the world in 16 locations.

We provide in-depth knowledge enabling you to master the increasingly rapid change process in the industry. Vocational outlines, software, machines and, especially, client requirements are all subject to a permanent and ongoing transformation. In the Print Media Academy you will acquire the competencies that you need for your success: From training on machines to management seminars, you will not just update and improve your professional knowledge, but also become qualified in “soft” factors such as the capacity for teamwork, team leadership and company management. Why not order our current seminar programme?

Notes

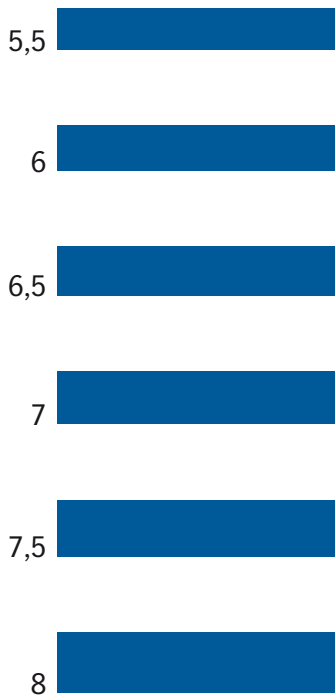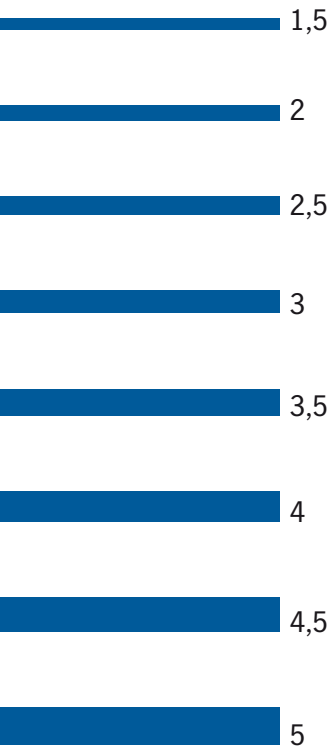

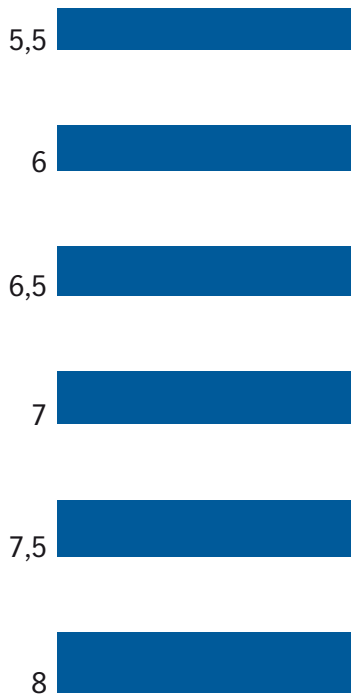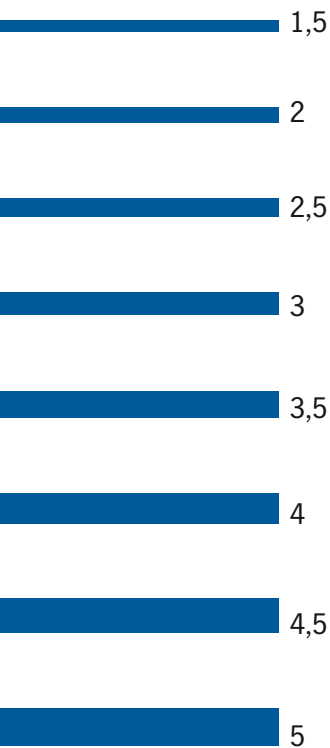

Heidelberger Druckmaschinen AG Print Media Academy

Kurfürsten-Anlage 52–60

69115 Heidelberg

Germany

Tel.: +49-62 21-92-0

Fax: +49-62 21-92-49 29

www.print-media-academy.com

Imprint

Platemaking: CtP

Printing: Speedmaster

Finishing: Stahlfolder, Stitchmaster

Fonts: Heidelberg Antiqua, Heidelberg Gothic

Printed in Germany

Trademarks

Heidelberg, Print Media Academy, and the Print Media Academy Logo are registered trademarks of Heidelberger Druckmaschinen AG in Germany and other countries.

Technical and other changes reserved. All information is presented without warranty. All liability for errors of information is barred.